

## CORROSION RESISTANCE OF ZINC IN WATER

### TECHNICAL BULLETIN CTB-5

Rev 4, November 2003


This issue supersedes all previous issues

Corrosion rates of zinc in natural fresh water are dependant on the type and condition of the water. Some of the variables which affect the corrosion rate are as follows:

1. Hard waters are normally less corrosive than soft waters due to protective calcium and magnesium based compounds which are deposited on the metal surface as scale.
2. As with other common metals the corrosion rate of zinc increases with aeration of the water. Dissolved oxygen and carbon dioxide both increase the corrosion rate of zinc.
3. Corrosive anion loading (*such as chlorides and sulphates*) will accelerate related corrosion mechanisms.
4. Agitation or stirring of water leads to increased corrosion, but attack is uniform. Under stagnant conditions or conditions of limited oxygen availability attack may be localised in the form of pits.
5. Zinc offers good corrosion resistance in water having a pH near neutral. The corrosion rate is low over the pH range 6.5 - 12 but increases rapidly towards the acid and alkaline sides of this range. See Figure 1. Most natural potable waters have a pH range from 5.0 to 8.5.
6. Figure 2 shows that as the temperature of still water rises above approximately 50°C the corrosion rate of zinc increases sharply and reaches a maximum at about 70°C, whereafter the rate decreases rapidly.

The increase in corrosion rate followed by a decrease is attributed to a change in the character of the corrosion product. A gelatinous adherent film is formed in the temperature range 20°-50°C, a granular flaky or non-adherent film between 50°-70°C and a compact dense film above 75°C, which becomes even more adherent with a further rise in temperature. At temperatures above 70°C a reversal of polarity can occur in aerated solutions. That is when the steel substrate is exposed, such as at a cut edge, it will actually begin to corrode to protect the zinc coating.


Figure 1: Effect of pH value on the corrosion rate of various metals.

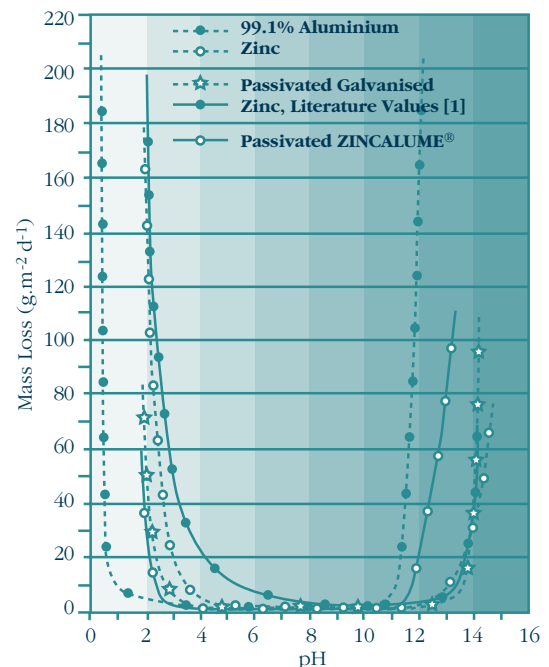

As a result of the variable nature of most natural waters due to increases in acid rain and salinity levels BlueScope Steel Limited only recommend the use of AQUAPLATE® polymer – coated steel to contain water. This product consists of a food grade polymer which is bonded to a galvanized steel substrate. Specific installation and design requirements have been made to cover the use of this product and these are contained in: Technical Bulletin TB-3 “The Manufacture of AQUAPLATE® Steel Water Tanks”.

ZINCALUME® zinc/aluminium alloy-coated steel and COLORBOND® prepainted steel, should not be used for the containment of water.

**Figure 2: Effect of Water Temperature on the corrosion rate of zinc**

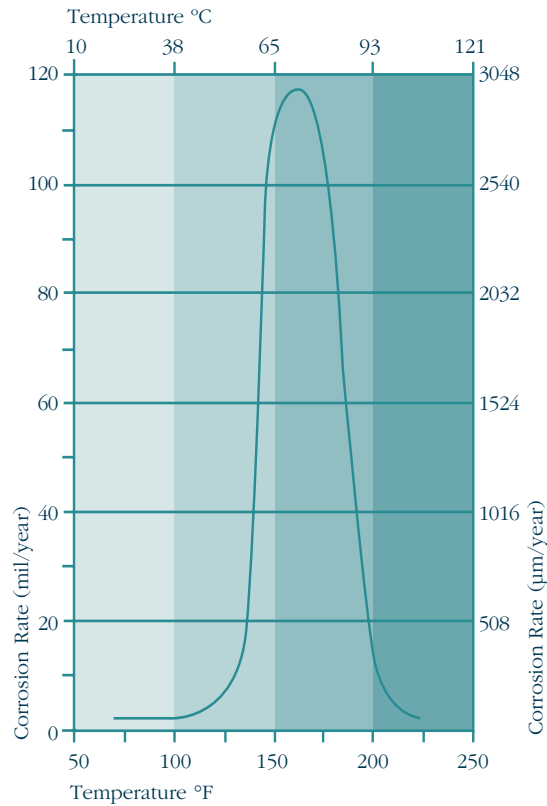

The information and advice contained in this Bulletin is of a general nature only, and has not been prepared with your specific needs in mind. You should always obtain specialist advice to ensure that the materials, approach and techniques referred to in this Bulletin meet your specific requirements.

BlueScope Steel Limited makes no warranty as to the accuracy, completeness or reliability of any estimates, opinions or other information contained in this Bulletin, and to the maximum extent permitted by law, BlueScope Steel Limited disclaims all liability and responsibility for any loss or damage, direct or indirect, which may be suffered by any person acting in reliance on anything contained in or omitted from this document.

COLORBOND®, ZINCALUME® and AQUAPLATE® are registered trade marks of BlueScope Steel Limited. BlueScope is a trade mark of BlueScope Steel Limited.

***Please ensure you have the current Technical Bulletin as displayed at [www.bluescopesteel.com.au](http://www.bluescopesteel.com.au)***

## BlueScope Steel

Copyright© 2003 BlueScope Steel Limited  
 BlueScope Steel Limited ABN 16 000 011 058  
 BlueScope Steel (AIS) Pty Ltd ABN 19 000 019 625



<b>AUSTRALIA</b>	SYDNEY	Telephone: (02) 9795 6700
	MELBOURNE	Telephone: (03) 9586 2222
	BRISBANE	Telephone: (07) 3845 9300
	ADELAIDE	Telephone: (08) 8243 7333
	PERTH	Telephone: (08) 9330 0666

<b>OVERSEAS</b>	BlueScope Steel (Malaysia) Sdn Bhd	Telephone: (603) 3250 8333
	BlueScope Steel (Thailand) Limited	Telephone: (66 38) 685 710
	PT BlueScope Steel Indonesia	Telephone: (62 21) 570 7564
	BlueScope Steel Southern Africa (Pty) Limited	Telephone: (27 21) 555 4265

